

ISSN 0141-5387 (PRINT)
ISSN 1460-2210 (ONLINE)

European Journal of Orthodontics

Volume 32 | Number 5 | October 2010

www.ejo.oxfordjournals.org



OXFORD JOURNALS
OXFORD UNIVERSITY PRESS



European Journal of Orthodontics

Published by the European Orthodontic Society

Scope

The *European Journal of Orthodontics* publishes (in English) research or clinical papers of interest to all orthodontists. Although the primary intention is to provide a forum for orthodontists in Europe, the journal welcomes papers from all parts of the world.

Editor

David Rice

Associate Editors

Tiziano Baccetti Dirk Bister Timo Peltomäki

Editorial Board

Selma Elekdağ-Türk

Ambra Michelotti

Piotr Fudalej

Perti Pirttiniemi

Demetrios J. Halazonetis

Yijin Ren

Anthony J. Ireland

Agneta Linder-Aronson Karsten

European Orthodontic Society

Officers of the Society

President 2010/2011:

Professor Nejat Erverdi

Hon. Secretary:

Professor Susan Cunningham

Hon. Treasurer:

Professor Andrej Zentner

President elect:

Professor David Suárez Quintanilla

Subscriptions

A subscription to the *European Journal of Orthodontics* comprises 6 issues. Prices include postage by surface mail, or for subscribers in the USA and Canada by airfreight, or in India, Japan, Australia and New Zealand, by Air Speeded Post. Airmail rates are available on request.

Annual Subscription Rate (Volume 32, 6 issues, 2010)

Institutional

Print edition and site-wide online access: £352.00/\$704.00/€528.00

Print edition only: £322.00/\$644.00/€483.00

Site-wide online access only: £284.00/\$568.00/€427.00

Personal

Print edition and individual online access: £249.00/\$498.00/€374.00

Please note: US\$ rate applies to US & Canada, Euros applies to Europe,

UK£ applies to UK and Rest of World

There may be other subscription rates available, for a complete listing please visit www.ejo.oxfordjournals.org/subscriptions/.

Full prepayment, in the correct currency, is required for all orders. Orders are regarded as firm and payments are not refundable. Subscriptions are accepted and entered on a complete volume basis. Claims cannot be considered more than FOUR months after publication or date of order, whichever is later. All subscriptions in Canada are subject to GST. Subscriptions in the EU may be subject to European VAT. If registered, please supply details to avoid unnecessary charges. For subscriptions that include online versions, a proportion of the subscription price may be subject to UK VAT. Personal rate subscriptions are only available if payment is made by personal cheque or credit card and delivery is to a private address.

The current year and two previous years' issues are available from Oxford University Press. Previous volumes can be obtained from the Periodicals Service Company, 11 Main Street, Germantown, NY 12526, USA. Email: psc@periodicals.com. Tel: +1 (518) 537 4700. Fax: +1 (518) 537 5899.

For further information, please contact: Journals Customer Service Department, Oxford University Press, Great Clarendon Street, Oxford OX2 6DP, UK. Email: jnl.cust.serv@oxfordjournals.org. Tel (and answerphone outside normal working hours): +44 (0)1865 353907. Fax: +44 (0)1865 353485. **In the US, please contact:** Journals Customer Service Department, Oxford University Press, 2001 Evans Road, Cary, NC 27513, USA. Email: jnlorders@oxfordjournals.org. Tel (and answerphone outside normal working hours): 800 852 7323 (toll-free in USA/Canada). Fax: 919 677 1714. **In Japan, please contact:** Journals Customer Services, Oxford University Press, Tokyo 4-5-10-8F Shiba, Minato-ku, Tokyo 108-8386 Japan. Email: custserv.jp@oxfordjournals.org. Tel: (03) 3813 1461. Fax: (03) 3818 1522.

Methods of payment. (i) Cheque (payable to Oxford University Press, to Oxford University Press, Cashiers Office, Great Clarendon Street, Oxford OX2 6DP, UK) in GB£ Sterling (drawn on a UK bank), US\$ Dollars (drawn on a US bank), or EU€ Euros. (ii) Bank transfer to Barclays Bank Plc, Oxford Group Office, Oxford (bank sort code 20-65-18) (UK), overseas only Swift code BARC GB 22 (GB£ Sterling to account no. 70299332, IBAN GB89BARC20651870299332; US\$ Dollars to account no. 66014600, IBAN GB27BARC20651866014600; EU€ Euros to account no. 7892365, IBAN GB16BARC20651878923655). (iii) Credit card (Mastercard, Visa, Switch of American Express).

European Journal of Orthodontics is published bimonthly in February, April, June, August, October and December by Oxford University Press, Oxford, UK. Annual subscription price is £352.00/\$704.00/€528.00. *European Journal of Orthodontics* is distributed by Mercury International, 365 Blair Road, Avenel, NJ 07001, USA. Periodicals postage paid at Rahway, NJ and at additional entry points.

US Postmaster: send address changes to *European Journal of Orthodontics* (ISSN 0141-5387), c/o Mercury International, 365 Blair Road, Avenel, NJ 07001, USA.

Permissions

For information on how to request permissions to reproduce articles/information from this journal, please visit www.oxfordjournals.org/permissions.

Advertising

Advertising, inserts and artwork enquiries should be addressed to Advertising and Special Sales, Oxford Journals, Oxford University Press, Great Clarendon Street, Oxford OX2 6DP, UK. Tel: +44 (0)1865 354767; Fax +44 (0)1865 353774; E-mail: jnladvertising@oxfordjournals.org

Oxford Journals Environmental and Ethical Policies

Oxford Journals is committed to working with the global community to bring the highest quality research to the widest possible audience. Oxford Journals will protect the environment by implementing environmentally friendly policies and practices wherever possible. Please see <http://www.oxfordjournals.org/ethicalpolicies.html> for further information on Oxford Journals' environmental and ethical policies.

© European Orthodontic Society 2010

All rights reserved; no part of this publication may be reproduced, stored in a retrieval system, or transmitted in any form or by any means, electronic, mechanical, photocopying, recording, or otherwise without prior written permission of the Publishers, or a licence permitting restricted copying issued in the UK by the Copyright Licensing Agency Ltd, 90 Tottenham Court Road, London W1P 9HE, or in the USA by the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923. For those in the USA or Canada not registered with CCC, articles can be obtained by fax in 48 hours by calling: WISE for Medicine™ 1-800-667-WISE.

Typeset by TNQ Books and Journals Pvt. Ltd., Chennai, India. Printed by Bell and Bain Ltd., Glasgow, UK.



Mixed Sources

Product group from well-managed forests and other controlled sources
www.fsc.org Cert no. TT-COC-002769
© 1996 Forest Stewardship Council

Contents

IN VITRO TOOTH CLEANING EFFICACY OF ELECTRIC TOOTHBRUSHES AROUND BRACKETS <i>MARC SCHÄTZLE, BEATRICE SENER, PATRICK R. SCHMIDLIN, THOMAS IMFELD AND THOMAS ATTIN</i>	481
FUNCTIONAL TREATMENT OF SNORING BASED ON THE TONGUE-REPOSITIONING MANOEUVRE <i>WILFRIED ENGELKE, WOLFGANG ENGELHARDT, MILAGROS MENDOZA-GÄRTNER, OSCAR DECCÓ, JENIFER BARRIRERO AND MICHAEL KNÖSEL</i>	490
COMPARISONS OF THE EFFECTS OF SYSTEMIC ADMINISTRATION OF L-THYROXINE AND DOXYCYCLINE ON ORTHODONTICALLY INDUCED ROOT RESORPTION IN RATS <i>ASLI BAYSAL, TANCAN UYSAL, SAIM OZDAMAR, BULENT KURT, GOKMEN KURT AND OMER GUNHAN</i>	496
EFFECTS OF THE ZYGOMA ANCHORAGE SYSTEM ON CANINE RETRACTION <i>ALEV ÇETİNŞAHİN, MÜFİDE DİNÇER, AYÇA ARMAN-ÖZÇİRPİCİ AND SİNA UÇKAN</i>	505
THREE-DIMENSIONAL GEOMETRIC MORPHOMETRICS APPLIED TO THE STUDY OF CHILDREN WITH CLEFT LIP AND/OR PALATE FROM THE NORTH EAST OF ENGLAND <i>I. BUGAIGHIS, P. O'HIGGINS, B. TIDDEMAN, C. MATTICK, O. BEN ALI AND R. HOBSON</i>	514
STRESS CHANGE ON THE TEMPOROMANDIBULAR JOINT IN MANDIBULAR PROGNATHISM SUBJECTS WITH ASYMMETRY AFTER ORTHOGNATHIC SURGERY <i>KOICHIRO UEKI, KIYOMASA NAKAGAWA, KOHEI MARUKAWA, ETSUHIDE YAMAMOTO AND NORIO TAKEUCHI</i>	522
ASSOCIATION BETWEEN NORMATIVE AND SELF-PERCEIVED ORTHODONTIC TREATMENT NEED AMONG 12- TO 15-YEAR-OLD STUDENTS IN SHIRAZ, IRAN <i>SHAHLA MOMENI DANAEI AND PARISA SALEHI</i>	530
A CONTROLLED EVALUATION OF ORAL SCREEN EFFECTS ON INTRA-ORAL PRESSURE CURVE CHARACTERISTICS <i>MICHAEL KNÖSEL, KLAUS JUNG, GERO KINZINGER, OSKAR BAUSS AND WILFRIED ENGELKE</i>	535
EVALUATION OF ORTHODONTIC TREATMENT AFTER 1 YEAR OF RETENTION—A RANDOMIZED CONTROLLED TRIAL <i>G. EDMAN TYNELIUS, L. BONDEMARK AND E. LILJA-KARLANDER</i>	542
REFERRAL PATTERNS OF DUTCH GENERAL DENTAL PRACTITIONERS TO ORTHODONTIC SPECIALISTS <i>BREGJE DE BONDT, IRENE H. A. AARTMAN AND ANDREJ ZENTNER</i>	548
VARIATIONS IN SURFACE CHARACTERISTICS AND CORROSION BEHAVIOUR OF METAL BRACKETS AND WIRES IN DIFFERENT ELECTROLYTE SOLUTIONS <i>CHIA-TZE KAO AND TSUI-HSIEN HUANG</i>	555
INFLUENCE OF DIFFERENT SELF-ETCHING PRIMERS ON THE BOND STRENGTH OF ORTHODONTIC LINGUAL BUTTONS <i>ROGELIO J. SCOUGALL-VILCHIS, SEITARO SAKU, HIROTOMO KOTAKE AND KOHJI YAMAMOTO</i>	561

Continued on inside back cover

Continued from outside back cover

ONE-COMPONENT SELF-ETCHING PRIMER: A SEVENTH GENERATION OF ORTHODONTIC BONDING SYSTEM? <i>MATHEUS MELO PITHON, ROGERIO LACERDA DOS SANTOS, ANTÔNIO CARLOS DE OLIVEIRA RUELLAS AND EDUARDO FRANZOTTI SANT'ANNA</i>	567
IN VITRO EVALUATION OF SHEAR BOND STRENGTHS OF COLOUR CHANGE ADHESIVES <i>HAKAN TÜRKKAHRAMAN, NECDET ADANIR, A. YALCIN GUNGOR AND HUSEYIN ALKIS</i>	571
THE INCIDENCE OF CANINE TRANSMIGRATION AND TOOTH IMPACTION IN A TURKISH SUBPOPULATION <i>ALI MURAT AKTAN, SAMI KARA, FARUK AKGÜNLÜ AND SIDDIK MALKOÇ</i>	575
MUTATIONAL ANALYSIS OF MSX1 AND PAX9 GENES IN PORTUGUESE FAMILIES WITH MAXILLARY LATERAL INCISOR AGENESIS <i>TERESA PINHO, ANABELA SILVA-FERNANDES, HASSAN BOUSBAA AND PATRÍCIA MACIEL</i>	582
VIRTUAL MODEL ANALYSIS AS AN ALTERNATIVE APPROACH TO PLASTER MODEL ANALYSIS: RELIABILITY AND VALIDITY <i>K. BOOTVONG, Z. LIU, C. MCGRATH, U. HÄGG, RICKY W. K. WONG, M. BENDEUS AND S. YEUNG</i>	589
INTERLEUKIN-1β LEVELS, PAIN INTENSITY, AND TOOTH MOVEMENT USING TWO DIFFERENT MAGNITUDES OF CONTINUOUS ORTHODONTIC FORCE <i>SUWANNEE LUPPANAPORNLARP, TAKASHI S. KAJII, RUDEE SURARIT AND JUNICHIRO IIDA</i>	596
BOOK REVIEWS	602
ANNOUNCEMENT	605

Influence of different self-etching primers on the bond strength of orthodontic lingual buttons

Rogelio J. Scougall-Vilchis*, Seitaro Saku**, Hirotomo Kotake** and Kohji Yamamoto**

*Department of Orthodontics, School of Dentistry, Autonomous University State of Mexico, Toluca City, Mexico and **Division of Oral Functional Sciences and Rehabilitation, School of Dentistry, Asahi University, Mizuho City, Gifu Prefecture, Japan

Correspondence to: Dr Rogelio J. Scougall-Vilchis, Department of Orthodontics, School of Dentistry, Autonomous University State of Mexico, Morelos ote. 1020 Col. San Sebastian, Toluca City, Mexico, 50090. E-mail: rogelio_scougall@hotmail.com

SUMMARY The aim of this study was to evaluate the influence of six self-etching primers (SEPs) on the shear/peel bond strength (SPBS) of orthodontic lingual buttons. A total of 150 extracted human premolars were randomly divided into six equal groups. In all groups, the lingual buttons were bonded with BeautyOrtho Bond™ and the enamel was conditioned with the following—group I (Control): Primers A & B™; group II: Transbond Plus SEP™; group III: Clearfil Mega Bond FA™; group IV: AdheSE™; group V: Peak SE & Peak LC Bond™; and group VI: Bond Force™. The teeth were stored at 37°C for 24 hours and the SPBS was tested (0.5 mm/minute). The results were calculated in mega pascals (MPa) and statistically analysed [mean, standard deviation, Scheffè, analysis of variance ($P < 0.05$)]. The adhesive remnant index (ARI) was also evaluated and statistically analysed with a chi-square test.

All groups demonstrated higher SPBS than the force suggested as necessary to accomplish orthodontic tooth movement, except group IV (7.7 ± 1.7 MPa), which showed a significantly lower value than groups I (10.7 ± 2.4 MPa), II (11.3 ± 3.1 MPa), and V (10.9 ± 2.8 MPa). The values of groups III (9.9 ± 1.6 MPa) and VI (10.5 ± 1.6 MPa) were comparable with those of groups I and V. Significant differences ($P < 0.05$) were found among the groups in ARI scores.

The SPBS values of all groups could be clinically acceptable and lingual buttons might be successfully bonded with any of these SEPs except AdheSE™ since that conditioner significantly influenced bond strength. As the SPBS was lower in all groups than the value at which enamel fractures have been found, a sound enamel surface might be left after removal of lingual buttons.

Introduction

Direct bonding of orthodontic brackets has been considered as one of the most significant developments in orthodontics during the past decades (D'Attilio *et al.*, 2005). The attachment of orthodontic brackets to the teeth is necessary for the treatment of malocclusions; however, the efficiency of orthodontic fixed appliances is dependent on having adequate bracket bond strength (Wong and Power, 2003). Currently, direct bonding with resin-based adhesives is the most popular method and the clinical standard for attaching orthodontic brackets to teeth (Dunn, 2007). However, despite the advances, demineralization around orthodontic brackets still remains a major problem for the patient (Polat *et al.*, 2005).

In response to the formation of white spot lesions, fluoride-releasing orthodontic adhesive systems (Scougall-Vilchis *et al.*, 2007) and self-etching primers (SEPs) have been introduced (Bishara *et al.*, 2001). Etching with self-etching compounds has proven effective despite the morphological variation of the interfacial properties of conventional and self-etched enamel. Some scanning electron microscopic (SEM) studies have shown that SEPs

result in shorter resin tags than conventional phosphoric acid, which nonetheless might be adequate for orthodontic bonding, because resin tag length is not a determinant of bond strength (Eliades, 2006). Consequently, the use of SEPs has increased and their quick and simplified technique has become popular (Paschos *et al.*, 2008).

Since bonding procedures have significantly improved, direct bonding of molar tubes and lingual buttons is frequently practiced in current orthodontics. The bond strength of orthodontic brackets has been widely tested; however, there are no recent studies of the bond strength of lingual buttons. Although Lalani *et al.* (2000) reported that *in vitro* lingual bond strengths are comparable with labial bond strengths, the bond strength of lingual buttons on lingual surfaces might be relevant because they are usually bonded to lingual rather than labial surfaces and the oral condition is completely different in this area, due to the higher risk of contamination with saliva. It is particularly important that the faster application of SEPs can reduce the risk of contamination and orthodontists require scientific evidence to select a suitable SEP for bonding lingual

buttons. Hence, this study was conducted to evaluate the influence of six SEPs on the shear/peel bond strength (SPBS) of orthodontic lingual buttons.

Materials and methods

Teeth

A total of 150 extracted human premolars were collected and stored in a solution of 0.2 per cent (w/v) thymol for 2 months. The teeth were previously used to test the bond strength of orthodontic brackets on labial surfaces (Scougall-Vilchis *et al.*, 2009); however, they were strictly selected with intact lingual surfaces following the criteria described by Bishara *et al.* (2005). The teeth were cleansed and pumiced using a rubber cup with fluoride-free paste for 10 seconds, after which they were thoroughly washed with water and air-dried.

Lingual buttons

Stainless steel lingual buttons (Tomy International, Tokyo, Japan) were used. The average surface area of the buttons base was 9.62 mm². This value was obtained by randomly measuring the base of 10 lingual buttons.

Bonding procedure

The teeth were randomly divided into six equal groups. In all groups, the lingual buttons were bonded with BeautyOrtho Bond™ (Shofu Inc., Kyoto, Japan), which is a fluoride-releasing orthodontic adhesive filled with surface pre-reacted glass ionomer particles. The lingual buttons were then light cured using a light-emitting diode light unit (BlueLEX™; Yoshida Dental, Tokyo, Japan) for a total of 20 seconds, with the entire procedure performed by the same author (RJS-V).

The enamel surfaces were conditioned as follows:

Group I (Control): The teeth were conditioned with two bottles of SEP (Primers A & B™ of BeautyOrtho Bond™, Shofu Inc.) according to the manufacturer's instructions. One drop of primer A (colourless) was mixed with one drop of primer B (red colour) until the mixture was homogeneous. The SEP was applied on the enamel surface, rubbed for 3 seconds, and lightly air-dried.

Group II: The teeth were conditioned with Transbond Plus SEP™ (3M Unitek, Monrovia, California, USA), which uses a lollipop system that has two compartments. Both compartments were squeezed to activate the product, after which the contents of each compartment were allowed to mix. The resulting mix was then applied by continuously rubbing the SEP on the enamel surface for 5 seconds. The SEP was then lightly dried using compressed air for 1–2 seconds.

Group III: The teeth were conditioned with Clearfil Mega Bond FA™ (Kuraray Medical, Tokyo, Japan) according to the manufacturer's instructions. This two-step SEP, which is generally used in operative dentistry, is considered the

first adhesive with antibacterial properties and has been introduced as Clearfil Protect Bond™ in other countries. The primer was applied on the enamel surface and 20 seconds later the surface was dried with a mild airflow. The bond was distributed evenly using a mild airflow and light cured for 10 seconds.

Group IV: The teeth were conditioned with AdheSE™ (Ivoclar Vivadent AG, Schaan, Liechtenstein) according to the manufacturer's instructions. AdheSE™ is a light-curing, self-etching two-component adhesive for enamel and dentine bonding, commonly used in restorative dentistry. The primer was applied on the tooth surface; once the enamel was completely coated, the primer was brushed over the entire surface for 15 seconds and dried with a strong stream of air until the mobile liquid film was no longer visible. The bond was applied and dispersed with a gentle stream of air, and light cured for 10 seconds.

Group V: The teeth were conditioned with Peak SE Primer™ (Ultradent™, South Jordan, Utah, USA) according to the manufacturer's instructions. This two-component SEP is commonly used in restorative dentistry. The chemical reaction was activated with a JetMix (syringe-in-syringe) delivery system. The conditioner was then applied on the enamel surface for 20 seconds using a brush tip with moderate pressure, and gently air-dried for 3 seconds. Immediately after, a thin coat of Peak LC Bond Resin™ (Ultradent™) was softly rubbed for 10 seconds onto the etched enamel with a spiral brush tip, gently air-dried, and light cured for 10 seconds.

Group VI: The teeth were conditioned with Bond Force™ (Tokuyama, Osaka, Japan) according to the manufacturer's instructions. This recently developed one-bottle SEP is indicated for bonding light-cure composite materials to uncut enamel. The conditioner was applied and rubbed onto the enamel for 20 seconds; the surface was gently dried with a continuous light air application for 5 seconds and blown with strong air for 5 seconds. The conditioner was then light cured for 10 seconds.

Storage

The teeth were fixed in acrylic resin (Orthodontic Resin; Dentsply Caulk International Inc., Philadelphia USA), with a label bearing the number of each sample. A mounting jig was used to align the lingual surface of the tooth so that it was perpendicular to the bottom of the mould and its lingual surface was parallel to the force during bond strength testing. Afterward, the teeth were stored in distilled water at 37°C for 24 hours.

SPBS test

A 0.036 inch stainless steel wire-loop was designed similar to that used by Mojtahedzadeh *et al.* (2006). The samples were tested using a universal testing machine (EZ Graph™, Shimadzu, Kyoto, Japan) in the shear/peel mode. The procedure was similar to the methods described by Oesterle *et al.* (2002) and Nemeth *et al.* (2006). Bond strengths were

then measured at a crosshead speed of 0.5 mm/minute and the force at fracture was recorded in Newton and converted into mega pascals (MPa).

Adhesive remnant index

Once the lingual buttons had been debonded, the enamel surface of each tooth was examined under $\times 10$ magnification with a stereomicroscope (Nikon, Tokyo, Japan), to determine the amount of residual adhesive remaining on each tooth. The adhesive remnant index (ARI) scores were recorded as described by Årtun and Bergland (1984), with the following scale used: 0 = no adhesive left on the tooth, 1 = less than half of the adhesive left on the tooth, 2 = more than half of the adhesive left on the tooth, and 3 = all adhesive left on the tooth, with a distinct impression of the button mesh.

Statistical analysis

Descriptive statistics including the mean, standard deviation, and Scheffé multiple comparisons (one-way analysis of variance) with significance predetermined at $P < 0.05$ were calculated for SPBS analysis. In addition, the chi-square test was used to evaluate the ARI.

SEM observation of enamel surfaces

The enamel surfaces conditioned with the SEPs were chemically prefixed with 2.5 per cent glutaraldehyde solution (4°C; 2 hours) and rinsed twice with cacodylate buffer (4°C; 20 minutes \times 2). They were then chemically fixed with 1 per cent OsO₄ solution (4°C; 1 hour) and rinsed twice with cacodylate buffer (4°C; 20 minutes \times 2). The specimens were then dehydrated in a graded series of ethanol, immersed in t-butanol (20 minutes \times 2), and freeze-dried (VFD-21S™; Vacuum Device, Ibaragi, Japan). Finally, the samples were placed on aluminium stubs, coated with osmium for 10 seconds (HPC-1S™; Vacuum Device), and observed under a SEM (S-4500™; Hitachi, Tokyo, Japan).

Results

Shear/peel bond strength

The SPBS, expressed in MPa, and descriptive statistics are shown in Table 1. All groups yielded higher SPBS than the force (5.9–7.8 MPa) considered by Reynolds and von Fraunhofer (1976), as sufficient to accomplish orthodontic tooth movement, except group IV (7.7 \pm 1.7 MPa), which showed a significantly lower value than groups I (10.7 \pm 2.4 MPa), II (11.3 \pm 3.1 MPa), and V (10.9 \pm 2.8 MPa). The values for groups III (9.9 \pm 1.6 MPa) and VI (10.5 \pm 1.6 MPa) were comparable with those of groups I and V.

Adhesive remnant index

The scores indicating the amount of adhesive remaining after debonding are presented in Table 2. Chi-square

comparison of the ARI scores among all groups ($\chi^2 = 35.42$) indicated that the groups were significantly different ($P = 0.0021$). The least amount of adhesive remnant was found in group IV. Comparable scores were found in groups II and VI; however, the amount of residual adhesive was slightly higher than that in groups I, III, and V.

SEM observation of enamel surfaces

Figure 1 shows the enamel surfaces viewed under a SEM after conditioning. The images of the surfaces conditioned with Primers A & B™ and Transbond Plus SEP™ (Figure 1b and 1c) show the effect produced by the conditioners directly on the enamel, while the images of the enamel surfaces conditioned with Clearfil Mega Bond FA™, AdheSE™, Peak SE & Peak LC Bond Resin™, and Bond Force™ (Figure 1d–1g) show the appearance of the enamel after the SEPs were light cured.

Discussion

Shear/peel bond strength

In view of the fact that orthodontic buttons are commonly bonded to lingual surfaces, human premolar teeth that were previously used to evaluate the bond strength of orthodontic brackets on labial surfaces (Scougall-Vilchis *et al.*, 2009) were

Table 1 Mean bond strength values (mega pascals) and descriptive statistics.

Group (SEP)	Mean \pm SD	Scheffé test*
I (Primers A & B™)	10.7 \pm 2.4	A
II (Transbond Plus SEP)	11.3 \pm 3.1	B
III (Clearfil Mega Bond FA™)	9.9 \pm 1.6	C
IV (AdheSE™)	7.7 \pm 1.7	A, B, and D
V (Peak SE & Peak LC Bond™)	10.9 \pm 2.8	D
VI (Bond Force™)	10.5 \pm 1.6	E

*Groups with the same letters are significantly different from each other.

Table 2 Distribution frequency and percentages of adhesive remnant index (ARI) scores.

Group (SEP)	ARI scores (%)				
	0	1	2	3	<i>n</i>
I (Primers A & B™)	3 (12)	20 (80)	2 (8)	0 (0)	25
II (Transbond Plus SEP)	5 (20)	12 (48)	6 (24)	2 (8)	25
III (Clearfil Mega Bond FA™)	2 (8)	23 (92)	0 (0)	0 (0)	25
IV (AdheSE™)	10 (40)	15 (60)	0 (0)	0 (0)	25
V (Peak SE & Peak LC Bond™)	10 (40)	11 (44)	2 (8)	2 (8)	25
VI (Bond Force™)	6 (24)	13 (52)	5 (20)	1 (4)	25

$\chi^2 = 35.428$; $df = 15$; $P = 0.0021$.

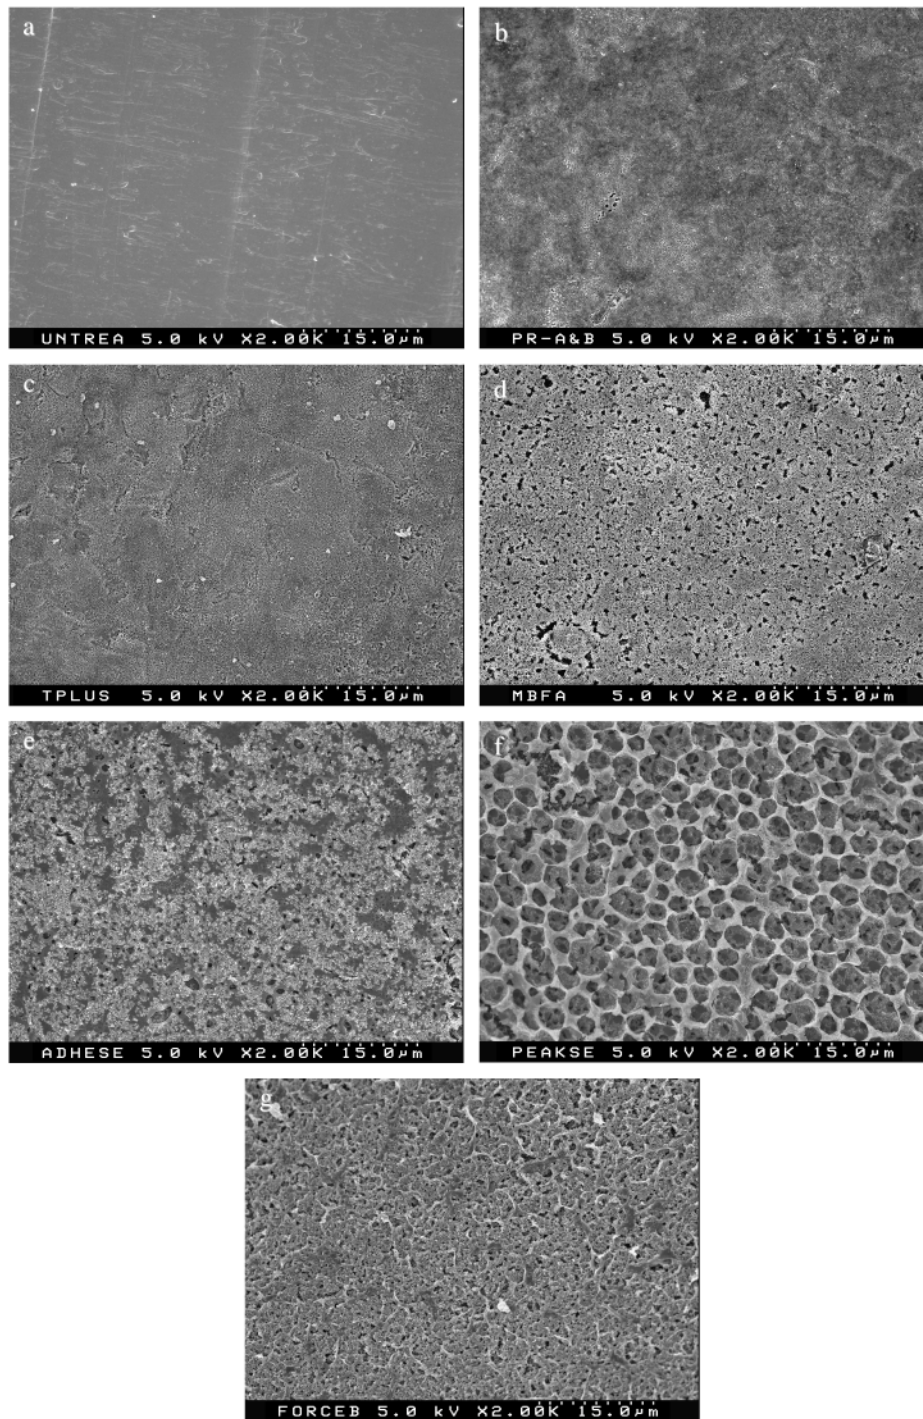


Figure 1 Scanning electron microscopic images of human enamel surfaces. (a) Unconditioned surface after pumicing with prophylactic paste and a rubber cup. Conditioned with self-etching primers (SEPs): (b) Primers A & B™ for 3 seconds (group I); (c) Transbond Plus SEP for 5 seconds (group II); (d) Clearfil Mega Bond FA™, primer applied for 20 seconds and light cured for 10 seconds (group III); (e) AdheSE™, primer applied for 30 seconds and light cured for 10 seconds (group IV); (f) peak SE Primer applied for 20 seconds and Peak LC Bond Resin™ rubbed for 10 seconds and light cured for 10 seconds (group V); (g) Bond Force™ applied for 20 seconds and light cured for 10 seconds (group VI).

used. They were preferred to test the SPBS of lingual buttons rather than freshly extracted bovine teeth (Oesterle *et al.*, 1998). This factor cannot affect the results because buttons are placed on lingual surfaces during orthodontic active treatment, when patients are wearing brackets on the labial surfaces. While Lalani *et al.* (2000) reported that *in vitro* lingual bond strengths are comparable with labial bond strengths and the parameter for labial and lingual bonding should be identical, the bond strength of buttons might be relevant because they are bonded to lingual rather than labial surfaces, and oral conditions such as higher humidity are different.

Under the conditions of this *in vitro* study, the SPBS in all groups might be considered clinically acceptable since the 'ideal' orthodontic bond strength is not merely the greatest bond strength possible; it should withstand orthodontic and masticatory forces, allow for easy bracket or lingual button removal when desired, and principally the force needed to remove the orthodontic attachment should be sufficiently low to prevent enamel fracture (Elvebak *et al.*, 2006).

Usually, BeautyOrtho Bond™ is used with two bottles of SEP (Primers A & B™); however, lingual buttons can be successfully bonded by combining this orthodontic adhesive with the other SEPs tested in this study, except AdheSE™, which had a significantly lower bond strength than groups I, II, and V. In this context, clinicians should consider that AdheSE™ is a two-step SEP and the chair-side time required is longer than that for one-step SEPs; nonetheless, it could be used as an alternative, but only when extremely light force is to be applied.

Group II (Transbond Plus SEP™) presented a slightly higher bond strength than the other groups but it should be borne in mind that this SEP and Primers A & B™ (group III) are both one-step SEPs marketed for orthodontic purposes, and they need to be applied for only 3 or 5 seconds. On the other hand, in group III the enamel was conditioned with Clearfil Mega Bond FA™, a two-step fluoride-releasing and antibacterial SEP (Korbmacher *et al.*, 2006; Attar *et al.*, 2007). This SEP has been recommended to reduce cariogenic bacteria around brackets and decrease the risk of demineralization (Attar *et al.*, 2007; Bulut *et al.*, 2007). Unfortunately, the application of fluoride-releasing conditioners or adhesives is contraindicated in patients with fluorosis or in those exposed to high concentrations of fluoride. In these cases the bonding procedure may need to be enhanced with additional bonding methods (Gange, 2006; Noble *et al.*, 2008). Peak SE & Peak LC Bond™ are two-step SEPs generally used in operative dentistry; additionally, Bond Force™ is a seventh-generation single-component SEP, fluoride-releasing bonding agent designed to be used on both cut/uncut enamel and dentine. To date, however, no previous studies have tested Peak SE & Peak LC Bond™ or Bond Force™ for orthodontic application. The results indicate that they could be successfully used with BeautyOrtho Bond™ for bonding lingual buttons as an alternative to 37 per cent H₃PO₄ or

other SEPs; however, the major disadvantage is the increased time required for application to the enamel surface.

The use of phosphoric acid has the advantage of increasing the bond strength of orthodontic brackets (Scougall-Vilchis *et al.*, 2007). Nevertheless, the application of SEP is recommended rather than 37 per cent H₃PO₄ to obtain a more conservative etch pattern and similar bond strength. In addition, SEPs have shown lower sensitivity to humidity than conventional phosphoric acid (dos Santos *et al.*, 2006), and this could be clinically relevant for bonding lingual buttons in which saliva contamination is 'expected', mainly in the lower arch.

Adhesive remnant index

A strong correlation between bond strength and adhesive remnant has been found (Scougall-Vilchis *et al.*, 2007). In this context, group IV presented the lowest SPBS as well as the lowest ARI scores both with significant differences. Moreover, it has been reported that the amount of adhesive remaining tends to be less when SEPs are used (Faltermeier *et al.*, 2007; Montasser *et al.*, 2008). In this study, groups I, III, and V presented lower ARI scores with the average amount of adhesive remaining being less than 50 per cent (score 1). This could be clinically advantageous since in those cases when the brackets fail at the enamel/adhesive interface, less residual adhesive remains and clean-up is likely to be easier and faster (Al Shamsi *et al.*, 2006). Conversely, higher amounts of adhesive remnants complicate clean up of the enamel and may also lead to surface scratches, cracking, and loss of sound enamel (Vicente *et al.*, 2006).

There were no enamel fractures after debonding, which could be explained by the fact that bond strength values were lower than 14 MPa in all groups, and the risk of enamel fractures increases when the force exceeds this value (Eminkahyagil *et al.*, 2006).

SEM observation of enamel surfaces

The application of SEPs is reported to produce a more conservative etch pattern than phosphoric acid (Summers *et al.*, 2004; Cal-Neto and Miguel, 2006). In this context, the sound surface of the untreated enamel changed slightly when it was conditioned with Primers A & B™ and Transbond Plus SEP™ (Figure 1b and 1c); however, the enamel conditioned with Primers A & B™ appeared similar to the untreated enamel. The enamel surface morphology when conditioned with two-step SEPs (AdheSE™, Peak SE & Peak LC Bond™, and Clearfil Mega Bond FA™), including Bond Force™ (one-bottle SEP), showed interesting differences (Figure 1d–1g). The conditioners left some microretentions on the enamel surface that enhanced bond strength. When the microretentions were greater, such as those produced by Peak SE & Peak LC Bond™, the SPBS tended to increase. Conversely, when microretentions were shallower, the bond strength was less (AdheSE™).

Conclusions

Within the limitations of this *in vitro* study, the following conclusions can be drawn:

1. The SPBS of orthodontic lingual buttons in all groups are clinically acceptable. However, application of AdheSE™ resulted in significantly lower bond strength.
2. The two newly tested materials for orthodontic use (Peak SE & Peak LC Bond™ and Bond Force™) have the disadvantage of the longer time required for application to the enamel.
3. Since SEPs present a gentler etch pattern, lower sensitivity to humidity, and suitable bond strengths, their application for bonding orthodontic lingual buttons is recommended.
4. Different SEPs can significantly affect the amount of residual adhesive, and the SEM images showed an interesting diversity of etch patterns.
5. In all cases, the mean SPBS values were lower than the value at which enamel fractures have been found; therefore, a sound enamel surface might be left after the removal of lingual buttons.

References

- Al Shamsi A, Cunningham J L, Lamey P J, Lynch E 2006 Shear bond strength and residual adhesive after orthodontic bracket debonding. *Angle Orthodontist* 76: 694–699
- Årtun J, Bergland S 1984 Clinical trials with crystal growth conditioning as an alternative to acid-etch enamel pretreatment. *American Journal of Orthodontics* 85: 333–340
- Attar N, Taner T U, Tulumen E, Korkmaz Y 2007 Shear bond strength of orthodontic brackets bonded using conventional vs one and two step self-etching/adhesive systems. *Angle Orthodontist* 77: 518–523
- Bishara S E, VonWald L, Laffoon J F, Warren J J 2001 Effect of a self-etch primer/adhesive on the shear bond strength of orthodontic brackets. *American Journal of Orthodontics and Dentofacial Orthopedics* 119: 621–624
- Bishara S E, Soliman M, Laffoon J, Warren J J 2005 Effect of antimicrobial monomer-containing adhesive on shear bond strength of orthodontic brackets. *Angle Orthodontist* 75: 397–399
- Bulut H, Turkun M, Turkun L S, Isiksal E 2007 Evaluation of the shear bond strength of 3 curing bracket bonding systems combined with an antibacterial adhesive. *American Journal of Orthodontics and Dentofacial Orthopedics* 132: 77–83
- Cal-Neto J P, Miguel J A 2006 Scanning electron microscopy evaluation of the bonding mechanism of a self-etching primer on enamel. *Angle Orthodontist* 76: 132–136
- D'Attilio M, Traini T, Di Iorio D, Varvara G, Festa F, Tecco S 2005 Shear bond strength, bond failure, and scanning electron microscopy analysis of a new flowable composite for orthodontic use. *Angle Orthodontist* 75: 410–415
- dos Santos J E, Quioca J, Loguercio A D, Reis A 2006 Six-month bracket survival with a self-etch adhesive. *Angle Orthodontist* 76: 863–868
- Dunn W J 2007 Shear bond strength of an amorphous calcium-phosphate-containing orthodontic resin cement. *American Journal of Orthodontics and Dentofacial Orthopedics* 131: 243–247
- Eliades T 2006 Orthodontic materials research and applications: Part 1. Current status and projected future developments in bonding and adhesives. *American Journal of Orthodontics and Dentofacial Orthopedics* 130: 445–451
- Elvebak B S, Rossouw P E, Miller B H, Buschang P, Ceen R 2006 Orthodontic bonding with varying curing time and light power using an argon laser. *Angle Orthodontist* 76: 837–844
- Eminkahyagil N, Arman A, Cetinsahin A, Karabulut E 2006 Effect of resin-removal methods on enamel and shear bond strength of rebonded brackets. *Angle Orthodontist* 76: 314–321
- Faltermeier A, Behr M, Müssig D 2007 A comparative evaluation of bracket bonding with 1-, 2-, and 3-component adhesive systems. *American Journal of Orthodontics and Dentofacial Orthopedics* 132: 144e1–e5
- Gange P 2006 Bonding in today's orthodontic practice. *Journal of Clinical Orthodontics* 40: 361–367
- Korbmacher H M, Huck L, Kahl-Nieke B 2006 Fluoride-releasing adhesive and antimicrobial self-etching primer effects on shear bond strength of orthodontic brackets. *Angle Orthodontist* 76: 845–850
- Lalani N, Foley T F, Voth R, Banting D, Mamandras A 2000 Polymerization with the argon laser: curing time and shear bond strength. *Angle Orthodontist* 70: 28–33
- Mojtahedzadeh F, Akhondi M S, Noroozi H 2006 Comparison of wire loop and shear blade as the 2 most common methods for testing orthodontic shear bond strength. *American Journal of Orthodontics and Dentofacial Orthopedics* 130: 385–387
- Montasser M A, Drummond J L, Evans C A 2008 Rebonding of orthodontic brackets. Part I, a laboratory and clinical study. *Angle Orthodontist* 78: 531–536
- Nemeth B R, Wiltshire W A, Lavelle C L 2006 Shear/peel bond strength of orthodontic attachments to moist and dry enamel. *American Journal of Orthodontics and Dentofacial Orthopedics* 129: 396–401
- Noble J, Karaiskos N E, Wiltshire W A 2008 *In vivo* bonding of orthodontic brackets to fluorosed enamel using an adhesion promoter. *Angle Orthodontist* 78: 357–360
- Oesterle L J, Newman S M, Shellhart W C 2002 Comparative bond strength of brackets cured using a pulsed xenon curing light with 2 different light-guide sizes. *American Journal of Orthodontics and Dentofacial Orthopedics* 122: 242–250
- Oesterle L J, Shellhart W C, Belanger G K 1998 The use of bovine enamel in bonding studies. *American Journal of Orthodontics and Dentofacial Orthopedics* 114: 514–519
- Paschos E, Westphal J O, Ilie N, Huth K C, Hickel R, Rudzki-Janson I 2008 Artificial saliva contamination effects on bond strength of self-etching primers. *Angle Orthodontist* 78: 716–721
- Polat O, Uysal T, Karaman A I 2005 Effects of a chlorhexidine varnish on shear bond strength in indirect bonding. *Angle Orthodontist* 75: 1036–1040
- Reynolds I R, von Fraunhofer J A 1976 Direct bonding of orthodontic brackets—a comparative study of adhesives. *British Journal of Orthodontics* 3: 143–146
- Scougall-Vilchis R J, Yamamoto S, Kitai N, Hotta M, Yamamoto K 2007 Shear bond strength of a new fluoride-releasing orthodontic adhesive. *Dental Materials Journal* 26: 45–51
- Scougall-Vilchis R J, Yamamoto S, Kitai N, Yamamoto K 2009 Shear bond strength of orthodontic brackets bonded with different self-etching adhesives. *American Journal of Orthodontics and Dentofacial Orthopedics* 136: 425–430
- Summers A, Kao E, Gilmore J, Gunel E, Ngan P 2004 Comparison of bond strength between a conventional resin adhesive and a resin modified glass ionomer adhesive: an *in vitro* and *in vivo* study. *American Journal of Orthodontics and Dentofacial Orthopedics* 126: 200–206
- Vicente A, Bravo L A, Romero M, Ortiz A J, Canteras M 2006 Effects of 3 adhesion promoters on the shear bond strength of orthodontic brackets: an *in-vitro* study. *American Journal of Orthodontics and Dentofacial Orthopedics* 129: 390–395
- Wong M, Power S 2003 A prospective randomized clinical trial to compare pre-coated and non-pre-coated brackets. *Journal of Orthodontics* 30: 155–158